



Hydrochar Derived from Sewage Sludge and Water Hyacinth and Its Characterization

Paul Sebastian, S^{a*}, E Parameswari^b, P. Kalaiselvi^c,
V. Davamani^d and M. Vijayakumar^a

^a Agricultural College and Research Institute, Tamil Nadu Agricultural University, Kudumiyamalai, Pudukkottai, Tamil Nadu, India.

^b Nammazhvar Organic Farming Research Centre, Tamil Nadu Agricultural University, Coimbatore, India.

^c ICAR - Krishi Vigyan Kendra, Tamil Nadu Agricultural University, Sandiyur, Salem, India.

^d Directorate of Natural Resource Management, Tamil Nadu Agricultural University, Coimbatore, India.

Authors' contributions

This work was carried out in collaboration among all authors. All authors read and approved the final manuscript.

Article Information

DOI: 10.9734/IJECC/2024/v14i44117

Open Peer Review History:

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/114877>

Original Research Article

Received: 29/01/2024

Accepted: 02/04/2024

Published: 15/04/2024

ABSTRACT

Population and urbanization increase the sewage generation. Sewage treatment plant (STP) generates the sewage sludge. Agricultural runoff and sewage water discharge into water bodies proliferates the growth of water hyacinth and creates environmental issues. Managing the sewage sludge and water hyacinth are difficult task because of high water content, environmental concerns, regulatory measures and high operational cost. Hydrothermal carbonization (HTC) converts the wet biomass into condensed solid product called hydrochar at moderate temperature range of 180 – 250°C under auto generated pressure. Through HTC process, the sewage sludge and water hyacinth were mixed and converted into hydrochar @ temperature of 200°C and 4h resident time

*Corresponding author: E-mail: paulsebastian.s@tnau.ac.in;

with L/S ratio of 9:1. The produced hydrochar showed desired functional groups viz., CH – methyl groups, C-O-C – alcohol groups, esters, ethers and Oxygenic functional groups (-C=O, -OH, -CO-O, C-O-C) with particle size of 494.8 nm, BET surface area of 369.70 m² g⁻¹, Zeta Potential of -27.9 mV. The hydrochar recorded slightly acidic pH (5.8) with appreciable levels of C (24.4%), N (2.51%), P (0.44%), K (0.98%), Ca (1.24%), Mg (0.68%). These properties of sewage sludge and water hyacinth derived hydrochar exhibits its potential use in agricultural and environmental applications.

Keywords: Sewage sludge; water hyacinth; hydrothermal carbonization; hydrochar.

1. INTRODUCTION

In India, the sewage sludge generation is about 19,127 t day⁻¹. It contains organic carbon (9.75-15.88%), Nitrogen (2.05-3.87%), Phosphorus (1.62-2.47%), Potassium (0.98-1.96%), Zn (1332.1-2584.6 mg kg⁻¹), Pb (309.6-608.5 mg kg⁻¹), Ni (125.5-388.5 mg kg⁻¹), Cu (136.6-451.7 mg kg⁻¹) and Cd (3.22-10.09 mg kg⁻¹) [1]. Water hyacinth weed occupies almost every waterbody and creates environmental problems. The multiplication rate is very high and reaches 125 t of wet biomass within 6-month period in 1 ha of area. The biomass contains carbon from 30-49%, cellulose from 30-40%, hemicellulose from 31-40% and lignin 10-15%. It contains total nitrogen of 1.12%, total phosphorus of 0.38%, total potassium of 1.24%, total calcium of 0.82% and total magnesium of 0.54% [1]. Due to the biochemical properties of the above said wastes viz., Sewage sludge and water hyacinth have the potential to synthesize the novel carbon material which is having multidimensional utility. This approach will give concurrent benefits in both disposal and obtaining high value products. Hydrothermal carbonization (HTC) is an emerging effective thermochemical process for production of hydrochar by converting wet biomass at relatively mild reaction temperatures i.e. 180-250°C and self-generated pressure into a coal-like material along with aqueous products and gases (primarily CO₂). Materials are having high water content (more than 90%), direct pyrolysis is not economically viable. Hence, it was treated using the hydrothermal carbonization (HTC) process. According to Garlapalli et al. [2], the low-quality hydrochar was improved by higher HTC temperature (260°C), followed by pyrolysis temperature (800°C) and the subsequent pyro-HTC char had the following characteristics: highest BET surface area (63.5 m² g⁻¹); mild basic pH (9.34); and no PAH and phenolic compounds. Mixed feedstock (40% corn silage + 30% grass silage + 30% cattle manure) digestate from a biogas plant was used to produce activated carbon. The HTC process

(temperature: 190-250°C; residence time: 3-6 h; pH: 5-7) converted the digestate into hydrochars, and it was chemically activated (impregnated with KOH) to enhance the surface area. The surface area increased from 8-14 m²g⁻¹ (hydrochars) to 930-1351 m²g⁻¹ (activated carbon). The activated carbon was a very effective adsorbent for carbon dioxide (CO₂) since it has large micropore volumes (0.35–0.50 cm³g⁻¹) [3]. Jin et al. [4] analyzed the conversion of digestate of swine manure and rice straw to hydrochar, and these materials were subjected to HTC-treatment at 190°C with a ratio of biomass and water at 1:4 and 1:9. The synthesized hydrochars were acidic, dissolved organic carbon, BET surface area, more O functional groups, and aromatic C=C and C-H band, when compared to the original feedstock and pyrochars. HTC is the promising technology for managing the sewage sludge and sewage sludge produced hydrochar is used in energy and agriculture (Kosińska et al., 2024). Sadish et al. [5] also studied the characterization of optimized hydrochar from paper board mill sludge using Response Surface Methodology. Phytotoxic property of hydrochar was eliminated by thermal treatment below 300°C [6]. Sludge hydrothermal carbonization resulted the P rich char (total P up to 25,175 mg kg⁻¹) but the free P were fixed in char but most of the free fractions were transformed and the hydrochar showed a high phosphate adsorption capacity (up to 23,815 mg kg⁻¹) and the adsorbed P could be readily released [7]. The wetland biomass wastes derived hydrochar had a moderate pH (5.0-7.7), more oxygen-containing groups, and higher energy density (18.0-27.1 MJ kg⁻¹) and high water-soluble P in biomass (71.0-73.2% of total P), more recalcitrant P species formed in hydrochar, implying that HTC treatment could achieve P immobilization and reduce P leaching loss. HTC is a promising treatment technique for wetland plants to produce valuable char with P reclamation [8]. Resident time and pH were greatly influence the production of hydrochar from water hyacinth [9].

Water hyacinth recorded hydrochar yield of 53.7% to 28.8% and HHV of 17.62 MJ kg⁻¹ to 20.93 MJ kg⁻¹ [9]. Co-hydrothermal carbonization (Co-HTC) process of sewage sludge and water hyacinth with addition of attapulgite @ 20% reduced the bioavailable form of Cu, Cr, Ni and increased the stable form [10]. Co-HTC of fecal sludge and water hyacinth @ 1:1 yielded biocrude yield of 33.47% and higher heating value of 29 MJ kg⁻¹ [11]. Co-HTC of Sewage sludge and banana stem are having efficient synergistic in heavy metals immobilization effects through converting from direct/potential eco-toxic fractions to non-toxic fraction [12]. Hydrochar production from waste biomass and high wet waste biomass is aided to achieve the Sustainable Development Goal (SDG) [13,14] since the produced hydrochar are used as an energy material [9,11,15,16], agricultural application [17,18] and environmental applications [19,20]. In this prelude this work has been taken to obtain hydrochar from the sewage sludge and water hyacinth biomass in order to find out the effective solution for managing the waste biomass.

2. MATERIALS AND METHODS

2.1 Hydrochar Production from ETP Sludge

Hydrochar, a product of Hydrothermal Carbonization is found to possess wide range of environmental and agricultural application. The purpose of this work is to produce the hydrochar from sewage treatment plant sludge and water hyacinth biomass and assess its efficiency in sodic soil reclamation. The materials used and methods adopted in these experiments are given below. In order to produce hydrochar, Sewage sludge was collected from Sewage Treatment Plant (STP) Ukkadam, Coimbatore and water hyacinth was collected from Koraiyar, Trichy. The sample of sewage sludge and water hyacinth were dried @ 105°C in oven, powdered sieved through 2 mm sieve and stored and their chemical properties were analyzed [21].

2.2 Characterization of Sewage Sludge, Water Hyacinth Biomass and Hydrochar

The Carbon, Hydrogen, Nitrogen and Sulphur composition were determined using Elemental Vario EL III CHNS analyser [22]. The surface texture and morphological features of the samples were identified by scanning electron microscope (M/s. FEI – Quanta 250, Czech

Republic) [23]. The internal morphology of the samples was determined by transmission electron microscope (M/S FEI - Technai Spirit G2) at an accelerating voltage of 120KV [23]. Fourier Transform Infrared Spectroscopy (FTIR) technique was used to determine the functional groups present in the sample [24]. The Particle size was measured in the particle size analyzer (Horiba Scientific Nanopartica SZ-100, Japan) [25]. The surface charges of sample were determined by measuring the zeta potential [26]. The BET surface area and pore volume were analyzed by Smartsorb 92/93 surface area analyzer under nitrogen environment [27,28]. In addition to this, the other essential characterizations were carried out as per the standard methods and the analytical data are presented in Table 1.

2.3 Production of Hydrochar from Sewage Sludge and Water Hyacinth Through Co-Hydrothermal Carbonization Process

Hydrochar, a carbonized material was produced from the raw sludge and water hyacinth by heating the material to different temperatures ranges (180°C, 200°C, 220°C, 240°C) and time 1hr, 2 hr, 4 hr and 6 hr) at self-generating pressure. Hydrochar production parameter optimization (Resident time and Temperature) was fixed by adopting RSM methodology. Sewage sludge and fresh water hyacinth biomass @ 1:1 ratio were mixed thoroughly before the experiment for attaining homogeneity. After homogenization, 90 g of sewage sludge and fresh water hyacinth (i.e., 9 g solids and 81g water) (maintained L/S ratio of 9:1 in HTC reactor) were taken in a 100 ml hydrothermal autoclave reactor and sealed. The reactor was then placed in the laboratory oven and heated to the specified temperatures for different reaction times. After the reaction has been completed, the reactor was removed immediately from the oven and placed in cold water to quench the reaction. The formed hydrochar was filtered through Whatman no. 40 filter paper to separate the solid and liquid portion, after that the suspended hydrochar was dried overnight at 105°C in oven and analysed [16].

2.4 Details of Experiment

In this experiment, four levels of different temperature and time periods were set for the production of hydrochar and it is presented in below.

List 1. Experimental design

| Factors | Levels | Level 1 | Level 2 | Level 3 | Level 4 |
|-------------|--------|---------|---------|---------|---------|
| Temperature | 4 | 180 °C | 200 °C | 220 °C | 240 °C |
| Time | 4 | 1h | 2h | 4h | 6h |

Number of Factors: 2 (Temperature & Time)

3. RESULTS AND DISCUSSION

3.1 Co-hydrothermal Carbonization of Sewage Sludge and Fresh Water Hyacinth Biomass

Based on the values of the individual responses and the predetermined optimization parameters (boundaries and goals), the optimization was carried out by the software. A set of optimized process parameters with presumed responses were generated after optimization. The predicted parameters with the highest desirability (towards 1) can be confirmed as an optimized run for the design. The process temperature of 200°C and time of 4h were shown a highest desirability and it was set as optimum process parameter for the production of hydrochar from Sewage sludge and fresh water hyacinth biomass. This was supported by Ferrentino et al. [29] Sabarish et al. [30] and Parameswari et al. [15]. The production of hydrochar from date palm waste for adsorbent preparation was optimized at 200°C for 2h [29]. Sabarish *et al.* (30) reported that the optimized parameter, 200°C for 4 h for hydrochar production from paper board mill sludge.

3.2 Characterization of Sewage Sludge and Fresh Water Hyacinth Biomass Derived Hydrochar

The physical, chemical, physico-chemical, proximate, ultimate and surface characterization of Sewage sludge and fresh water hyacinth derived hydrochar (Plate 1) were analysed and their results are presented in Table 1. The production of acidic groups like acetic acid, glycolic acid, formic acid, and levulinic acid as a result of the breakdown of organic molecules depicted the acidic pH of the Hydrochar [4]. The Structural and morphological characteristics of Sewage sludge and water hyacinth derived Hydrochar (SSWHH) were given in table 2. The zeta potential value of hydrochar was decreased. The establishment of cross-linking electrophilic bonds with oxygenic functional groups (OFG) (hydroxyl, carboxylic and phenolic) through the surface deprotonation, explains the decrease in

surface's zeta potential. The structural features like surface area and pore volume of the hydrochar produced showed the increase in surface area and pore volume. The findings of Sadish et al. [5] revealed the same as the HTC reaction resulted in reduced oxygen, hydrogen, nitrogen and sulfur content with increase in carbon content. Similar results were also reported by Wang et al. [31], Ramesh et al. [32], Marx and van der Merwe [33], Sabarish et al. [30] and Parameswari et al. [15].

3.3 FTIR Spectra Analysis

FTIR spectral analysis (Fig. 1) reveals that depicts to the presence inter/intra-hydrogen bonded (O-H) stretching vibration of alcohols, phenols, and carboxylic acids as in cellulose and lignin, which indicating the presence of free hydroxyl groups on the surface. In addition to this, the hydrochar is having other functional groups *viz.*, -CH – methyl groups, C-O-C – alcohol groups, esters, ethers and Oxygenic functional groups (-C=O, -OH, -CO-O, C-O-C). Dehydration, polymerization reaction and aromatization are increased the functional groups in hydrochar. The presence of the functional groups was supported by Reza [34], Saha et al. [35], Nguyen et al. [36], Sabarish et al. [30], Parameswari *et al.* [15].

3.4 Analysis of Structural Morphology

SEM image (Fig. 2) revealed that, hydrochar showed rougher surface, small cracks, fissures, pores, and grooves which indicates the existence of a linked porous network of surfaces. These rough surface morphologies were clearly apparent in micrographs, which also showed particle size decrease from μm to nm (hydrochar). In addition to that, the hydrochar surface from micrographs revealed the particle dispersions in the form of spongy, spherical shaped particles, fluffy and fuzzy nature with deeper fragmentation. The TEM images (Fig. 2) portrayed the formation of porous – spherical, hexagonal, tubular, and microsphere carbons. spherical and tubular porous carbon (carbon nanotube) materials were formed from the irregular shaped precursor particles. Oumabady *et al.* (2020) reported that the surface morphologies of paper board mill ETP sludge

(PBM-ETP) and PBM-ETP sludge derived hydrochar showed the smooth and coarser surface, respectively. The formation of the rougher surface with microspheres on the surface of PBSH was due to the decomposition of easily degradable compound hemicellulose and cellulose followed by softening of lignin [37,30,15,38].

Table 1. Characteristics of raw sewage sludge, water hyacinth, and sewage sludge and water hyacinth derived Hydrochar (SSWHH)

| Parameters | Sewage sludge | Water hyacinth | SSWHH |
|------------------------------------|---------------|----------------|--------|
| pH | 6.01 | 6.68 | 5.80 |
| EC (dS m ⁻¹) | 3.70 | 1.72 | 3.00 |
| C (%) | 19.32 | 29.42 | 24.40 |
| H (%) | 2.66 | 5.56 | 3.28 |
| N (%) | 2.28 | 2.66 | 2.51 |
| S (%) | 0.99 | 0.73 | 0.97 |
| P (%) | 0.58 | 0.38 | 0.44 |
| K (%) | 1.70 | 1.24 | 0.98 |
| Ca (%) | 1.80 | 0.82 | 1.24 |
| Mg (%) | 1.20 | 0.54 | 0.68 |
| Metals (mg kg⁻¹) | | | |
| Cadmium | 0.64 | 1.80 | 0.76 |
| Chromium | 6.5 | BDL | 1.80 |
| Nickel | 12.55 | BDL | 0.88 |
| Lead | 30.9 | BDL | 0.92 |
| Iron | 560 | 320.00 | 436.0 |
| Zinc | 980 | 37.6 | 440.00 |

Table 2. Structural morphology and textural characterization of Hydrochar produced from sewage sludge and water hyacinth

| Parameters | Value |
|--|--------|
| BET Surface Area (m ² g ⁻¹) | 369.70 |
| Pore Volume (cc g ⁻¹) | 0.6790 |
| Particle Size (nm) | 494.8 |
| Zeta Potential (mV) | -27.9 |



Plate 1. Hydrochar produced from sewage sludge and water hyacinth

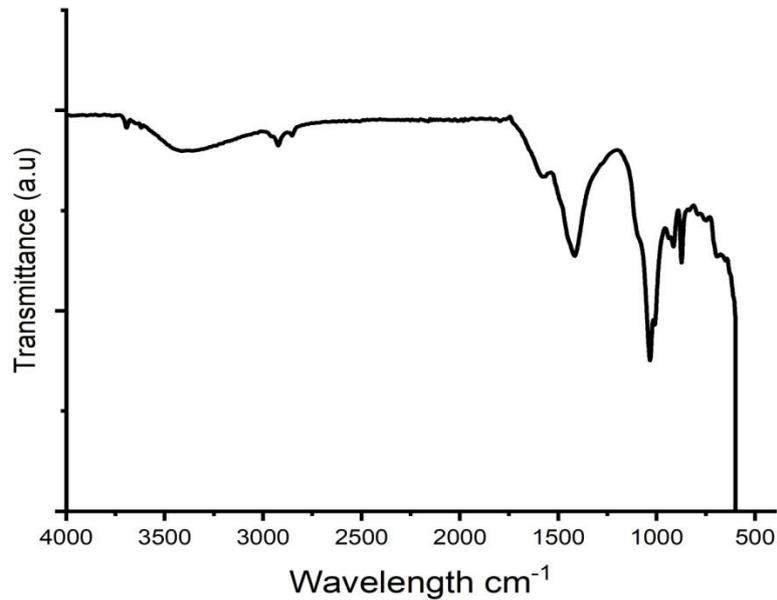


Fig. 1. FTIR Spectra of Hydrochar produced from sewage sludge and water hyacinth

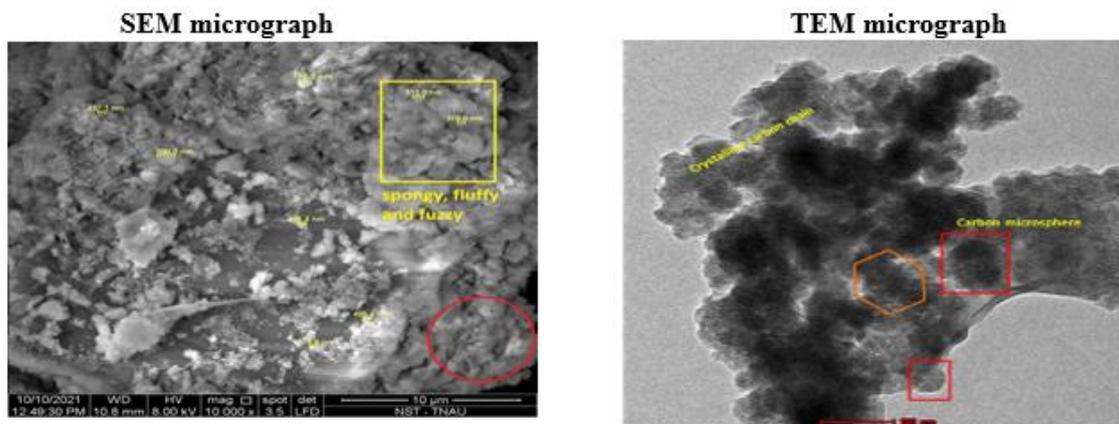


Fig. 2. Structural morphology of Hydrochar produced from sewage sludge and water hyacinth

4. CONCLUSION

Based on the results obtained by the laboratory experiments, it could be concluded that the ideal parameters were set as 200°C temperature and 4h residence time for production of hydrochar from Sewage sludge and water hyacinth at self-generating pressure. The characteristics features of produced hydrochar like pH, C, S, N, P, K, Ca, Mg, BET surface area, particle size and zeta potential are showed the positive to used agricultural soil amendment and environmental application. This approach is used to convert the high wet organic waste materials into valuable carbon material as hydrochar.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

- 1 Saha Sushanta, Saha Bholanath, Hazra Gora, Pati Sajal, Pal Biplab, Kundu Dipa, Bag Animesh, Chatterjee Nitin, Batabyal Kaushik. Assessing the suitability of sewage-sludge produced in Kolkata, India for their Agricultural Use. 2018;84: 781-792. Available:10.16943/ptinsa/2018/49410.

- 2 Garlapalli RK, Wirth B, Reza MT. Pyrolysis of hydrochar from digestate: Effect of hydrothermal carbonization and pyrolysis temperatures on pyrochar formation. *Bioresource Technology*. 2016;220:168-174.
- 3 Rodriguez Correa C, Bernardo M, Ribeiro RPPL, Esteves IAAC, Kruse A. Evaluation of hydrothermal carbonization as a preliminary step for the production of functional materials from biogas digestate. *Journal of Analytical and Applied Pyrolysis*. 2017;124:461-474.
- 4 Jin H, Sun E, Xu Y, Guo R, Zheng M, Huang H, Zhang S. Hydrochar derived from anaerobic solid digestates of swine manure and rice straw: A potential recyclable material. *BioResources* 2018;13:1019-1034.
- 5 Sadish O, Paul Sebastian S, Sara Parwin Banu K, Mahendran R. Hydrochar as an energy alternative to coal: Effect of temperature on hydrothermal carbonization of paper board mill sludge. *International Journal of Current Microbiology and Applied Sciences*. 2019;8(6):1668-1675.
- 6 Hitzl M, Mendez A, Owsianiak M, Renz M. Making hydrochar suitable for agricultural soil: A thermal treatment to remove organic phytotoxic compounds. *Journal of Environmental Chemical Engineering*. 2018;6(6):7029-7034. Available:<https://doi.org/10.1016/j.jece.2018.10.064>
- 7 Fei YH, Zhao D, Cao Y, Huot H, Tang YT, Zhang H, Xiao T. Phosphorous retention and release by sludge-derived hydrochar for potential use as a soil amendment. *Journal of Environmental Quality*. 2019;48(2):502-509.
- 8 Cui X, Lu M, Khan MB, Lai C, Yang X, He Z, Yan B. Hydrothermal carbonization of different wetland biomass wastes: Phosphorus reclamation and hydrochar production. *Waste management*. 2020;102:106-113.
- 9 Zhang C, Ma X, Chen X, Tian Y, Zhou Y, Lu X, Huang T. Conversion of water hyacinth to value-added fuel via hydrothermal carbonization. *Energy*. 2020;197:117193.
- 10 Qi X, Ma X, Yu Z, Lu X, Liang S, Teng W. Addition of water hyacinth and attapulgitite during hydrothermal carbonization of sewage sludge: Migration behavior of heavy metals and fuel characteristics of hydrochar. *Journal of Environmental Chemical Engineering*. 2022;10(6):108857.
- 11 Opu RK, Hossain MR, Monir MSH, Shanto RH, Osman MS. Co-liquefaction of faecal sludge and water hyacinth: Exploring the fuel characteristics of biocrude including thermal maturation and petroleum fractionation. *Biomass and Bioenergy*. 2023;173:106785.
- 12 Zhang C, Zheng C, Ma X, Zhou Y, Wu J. Co-hydrothermal carbonization of sewage sludge and banana stalk: fuel properties of hydrochar and environmental risks of heavy metals. *Journal of Environmental Chemical Engineering*. 2021;9(5):106051.
- 13 Kassim FO, Sohail M, Taylor B, Afolabi OO. Hydrothermal carbonisation of mixed agri-food waste: Process optimisation and mechanistic evaluation of hydrochar inorganic chemistry. *Biomass and Bioenergy*. 2024;180:107027.
- 14 Tran TK, Huynh L, Nguyen HL, Nguyen MK, Lin C, Hoang TD, Hung NTQ, Nguyen XH, Chang SW, Nguyen DD. Applications of engineered biochar in remediation of heavy metal (loid) s pollution from wastewater: Current perspectives toward sustainable development goals. *Science of The Total Environment*. 2024;171859.
- 15 Parameswari E, Paul Sebastian S, Blessy Monica K, Davamani V, Kalaiselvi P, Ilakiya T. Hydro thermal carbonization (HTC) of sewage sludge: Process optimization through RSM and assessing its energy potential. *Bioremediation Journal*. 2023;1-15.
- 16 Sadish O, Paul Sebastian S, PS. Kamaludeen SP, Ramasamy M, Kalaiselvi P, Parameswari E. Preparation and characterization of optimized hydrochar from paper board mill sludge. *Scientific reports*. 2020;10(1):773.
- 17 Khosravi, A, Yuan Y, Liu Q, Zheng H, Hashemi M, Tang Y, Xing B. Hydrochars as slow-release phosphorus fertilizers for enhancing corn and soybean growth in an agricultural soil. *Carbon Research*. 2024;3(1):1-19.
- 18 Ding S, Li J, Wang Y, He S, Xie H, Fu H, Feng Y, Shaheen SM, Rinklebe J, Xue L. Manure derived hydrochar reduced phosphorus loss risk via an alteration of phosphorus fractions and diversified microbial community in rice paddy soil.

- Science of The Total Environment. 2024;918:170582.
- 19 Petrović J, Ercegović M, Simić M, Koprivica M, Dimitrijević J, Jovanović A, Janković Pantić J. Hydrothermal Carbonization of Waste Biomass: A Review of Hydrochar Preparation and Environmental Application. *Processes*. 2024;12(1):207.
- 20 Jalilian M, Bissessur R, Ahmed M, Hsiao A, He QS, Hu Y. A review: Hydrochar as potential adsorbents for wastewater treatment and CO₂ adsorption. *Science of The Total Environment*. 2024;169823.
- 21 Lin Y, Ma X, Peng X, Hu S, Yu Z, Fang S. Effect of hydrothermal carbonization temperature on combustion behavior of hydrochar fuel from paper sludge. *Applied thermal engineering*. 2015;91:574-582.
- 22 Kalderis D, Tsuchiya S, Phillipou K, Paschalidou P, Pashalidis I, Tashima D, Tsubota T. Utilization of pine tree biochar produced by flame-curtain pyrolysis in two non-agricultural applications. *Bioresource Technology Reports*. 2020;9:100384. DOI:<https://doi.org/10.1016/j.biteb.2020.100384>
- 23 Kliewer CJ, Bieri M, Somorjai GA. Hydrogenation of the α , β -unsaturated aldehydes acrolein, crotonaldehyde, and prenal over Pt single crystals: A kinetic and sum-frequency generation vibrational spectroscopy study. *Journal of the American Chemical Society*. 2009;131(29):9958-9966.
- 24 Trakal L, Šigut R, Šillerová H, Faturíková D, Komárek M. Copper removal from aqueous solution using biochar: effect of chemical activation. *Arabian Journal of Chemistry*. 2014;7(1):43-52.
- 25 Kuzniatsova TA, Mottern ML, Chiu WV, Kim Y, Dutta PK, Verweij H. Synthesis of thin, oriented zeolite membranes on a macroporous support. *Advanced Functional Materials*. 2008;18(6):952-958.
- 26 Asadi A, Huat BB, Shariatmadari N. Keeping electrokinetic phenomena in tropical peat into perspective. 2009; 29:281-288.
- 27 Brunauer S, Emmett PH, Teller E. Adsorption of gases in multimolecular layers. *Journal of the American Chemical Society*. 1938;60(2):309-319.
- 28 Yang J, Qiu K. Preparation of activated carbons from walnut shells via vacuum chemical activation and their application for methylene blue removal. *Chemical Engineering Journal*. 2010;165(1):209-217. DOI:<https://doi.org/10.1016/j.cej.2010.09.019>.
- 29 Ferrentino R, Ceccato R, Marchetti V, Andreottola G, Fiori L. Sewage sludge hydrochar: An option for removal of methylene blue from wastewater. *Applied Sciences*. 2020;10(10):3445.
- 30 Sabarish K, Paul Sebastian S, Maheswari M, Balasubramaniam P, Ejilane J. Production and characterization of paper board mill ETP sludge derived hydrochar. *International Journal of Environment and Climate Change*. 2021;11(11):1-8.
- 31 Wang B, Fu H, Han L, Xie H, Xue L, Feng Y, Xing B. Physicochemical properties of aged hydrochar in a rice-wheat rotation system: A 16-month observation. *Environmental Pollution*. 2021;272: 116037.
- 32 Ramesh S, Sundararaju P, Banu KSP, Karthikeyan S, Doraiswamy U, Soundarapandian K. Hydrothermal Carbonization of arecanut husk biomass: fuel properties and sorption of metals. *Environmental Science and Pollution Research*. 2019;26(4):3751-3761.
- 33 Marx S, van der Merwe K. Utilization of hydrochar derived from waste paper sludge through hydrothermal liquefaction for the remediation of phenol contaminated industrial wastewater. *Water Practice and Technology*; 2021.
- 34 Reza MT. Upgrading biomass by hydrothermal and chemical conditioning: University of Nevada, Reno; 2013.
- 35 Saha N, Saba A, Reza MT. Effect of hydrothermal carbonization temperature on pH, dissociation constants, and acidic functional groups on hydrochar from cellulose and wood. *Journal of Analytical and Applied Pyrolysis*. 2019;137:138-145.
- 36 Nguyen LH, Van HT, Chu THH, Nguyen THV, Nguyen TD. Paper waste sludge-derived hydrochar modified by iron (III) chloride for enhancement of ammonium adsorption: An adsorption mechanism study. *Environmental Technology & Innovation*. 2021;21:101223.
- 37 Boyjoo Y, Cheng Y, Zhong H, Tian H, Pan J, Pareek VK, Lamonier JF, Jaroniec M, Liu J. From waste Coca Cola® to activated carbons with impressive capabilities for

- CO₂ adsorption and supercapacitors. Carbon. 2017;116:490-499.
- 38 Kosińska N, Krzyżyńska R, Ghazal H, Jouhara H. Hydrothermal carbonisation of sewage sludge and resulting biofuels as a sustainable energy source. Energy. 2023; 127337.

© Copyright (2024): Author(s). The licensee is the journal publisher. This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:

<https://www.sdiarticle5.com/review-history/114877>